

Conventional High-Speed Steel Evoloop® M4

ERASTEEL

Evoloop® M4 is a vanadium based grade used for cold work applications.

STANDARDS

- > EN 10027-1: HS 6-5-4
- > EN 10027-2: 1.3351
- > FRANCE: AFNOR X135WMoCrV 6-5-4-4

- > ASTM: AISI M4
- > JAPAN: JIS SKH54

DELIVERY HARDNESS

- > Typical soft annealed hardness is 250 HB
- > Cold-drawn and cold-rolled material is typically 10-40 HB harder

CHEMICAL COMPOSITION

Safety datasheet available

C	Cr	Mo	W	Co	V
1.30	4.2	4.5	5.6	-	4.0

APPLICATIONS

- > Punches
- > Form tools
- > Rolls
- > Broaches inserts
- > Dies

FORM SUPPLIED

- > Drawn wire
- > Round bars
- > Flat bars
- > Square bars

Available surface conditions: hot rolled, drawn, round, peeled, turned.

HEAT TREATMENT


- > Soft annealing in a protective atmosphere at 850-900°C for 3 hours, followed by slow cooling 10°C per hour down to 700°C, then air cooling.
- > Stress-relieving at 600°C to 700°C for approximately 2 hours, slow cooling down to 500°C.
- > Hardening in a protective atmosphere with pre-heating in 2 steps at 450-500°C and 850-900°C and austenitising at a temperature suitable for chosen working hardness.
- > Tempering at 560°C twice for at least 1 hour each time.

PROCESSING

Evoloop® M4 can be worked as follows:

- > machining (grinding, turning, milling)
- > polishing
- > hot forming
- > electrical discharge machining
- > welding (special procedure including preheating and filler materials of base material composition)

GUIDELINES FOR HARDENING

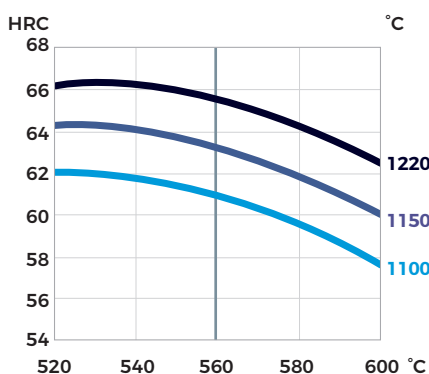

Tempering temperature in °C

Hardness after hardening, quenching and tempering 2 x 1 hour

GRINDING

During grinding, local heating of the surface, which may alter the temper, must be avoided. Grinding wheel manufacturers can provide advice on the choice of grinding wheels.

SURFACE TREATMENT

The steel grade is a perfect substrate material for PVD coating. If nitriding is requested, a small diffusion zone is recommended but avoid compound and oxidized layers.


Tool	Hardening	Tempering
Single-edge cutting tools	1220°C	550-570°C
Multi-edge cutting tools	1100-1220°C	550-570°C
Cold work tools	1100-1180°C	550-570°C

PROPERTIES

PHYSICAL PROPERTIES

Temperature	20°C
Density g/cm ³	8.0


IMPACT TOUGHNESS

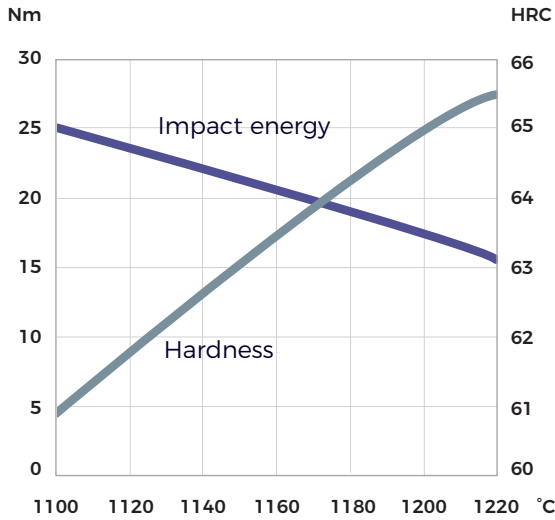

Hardening temperature in °C

Tempering 2 x 1 hour at 560°C
Unnotched test piece 7 x 10 x 55 mm

4-POINT BEND STRENGTH

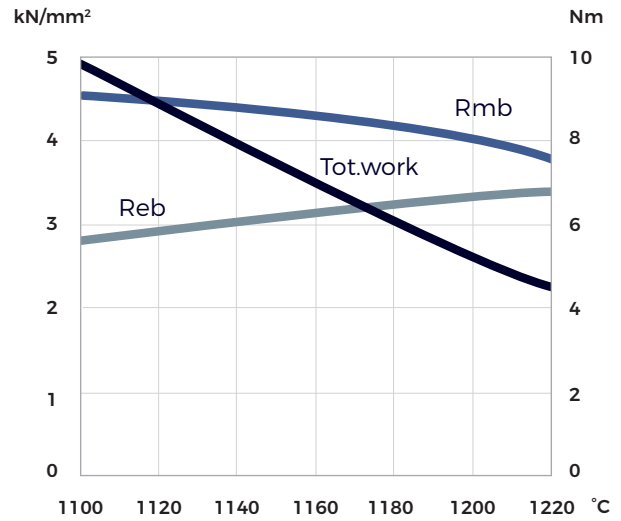

Hardening temperature in °C

Tempering 2 x 1 hour at 560°C
Dimension of test piece Ø 4.7 mm

Rmb = Ultimate bend strength in kN/mm²
Reb = Bend yield strength in kN/mm²
Tot. work = Total work in Nm

COMPARATIVE PROPERTIES

