

# Conventional High-Speed Steel Evoloop® MATII

# ERASTEEL

**Evoloop® MATII is a High-Speed Steel with excellent toughness combined with a good heat resistance.**

## STANDARDS

- > EN 10027-1: HS 1-5-1-8
- > EN 10027-2: 1.3270

## DELIVERY HARDNESS

- > Typical soft annealed hardness is 240 HB
- > Cold-drawn and cold-rolled material is typically 10-40 HB harder

## CHEMICAL COMPOSITION

Safety datasheet available

C	Cr	Mo	W	Co	V
0.72	4.0	5.0	1.0	8.0	1.0

## APPLICATIONS

- > Bi-metal saws
- > Bandsaws
- > Sabre saws

## FORM SUPPLIED

- > Bi-metal edges
- > Strips

Available surface conditions: cold-rolled.

## HEAT TREATMENT


- > Soft annealing in a protective atmosphere at 850-900°C for 3 hours, followed by slow cooling 10°C per hour down to 700°C, then air cooling.
- > Stress-relieving at 600°C to 700°C for approximately 2 hours, slow cooling down to 500°C.
- > Hardening in a protective atmosphere with pre-heating in 2 steps at 450-500°C and 850-900°C and austenitising at a temperature suitable for chosen working hardness.
- > Tempering at 560°C twice for at least 1 hour each time. Cooling to room temperature < 25°C between tempering

## PROCESSING

Evoloop® MATII can be worked as follows:

- > machining (grinding, turning, milling)
- > polishing
- > hot forming
- > electrical discharge machining
- > welding (special procedure including preheating and filler materials of base material composition)

## GUIDELINES FOR HARDENING

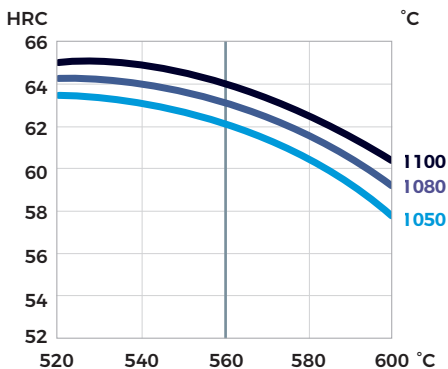

Tempering temperature in °C

Hardness after hardening, quenching and tempering 2 x 1 hour

## GRINDING

During grinding, local heating of the surface, which may alter the temper, must be avoided. Grinding wheel manufacturers can provide advice on the choice of grinding wheels.

## SURFACE TREATMENT

The steel grade is a perfect substrate material for PVD coating. If nitriding is requested, a small diffusion zone is recommended but avoid compound and oxidized layers.


Tool	Hardening	Tempering
Saws	1050-1100°C	550-570°C

**PROPERTIES**

**PHYSICAL PROPERTIES**

Temperature	20°C
Density g/cm <sup>3</sup>	7.9


**IMPACT TOUGHNESS**

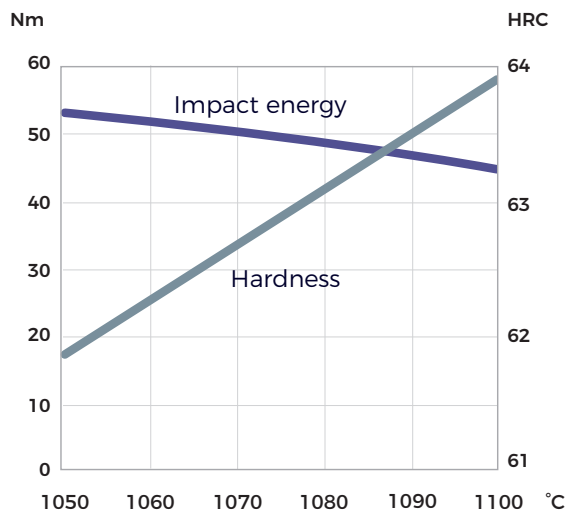

Hardening temperature in °C

Tempering 2 x 1 hour at 560° C  
Unnotched test piece 7 x 10 x 55 mm

**4-POINT BEND STRENGTH**

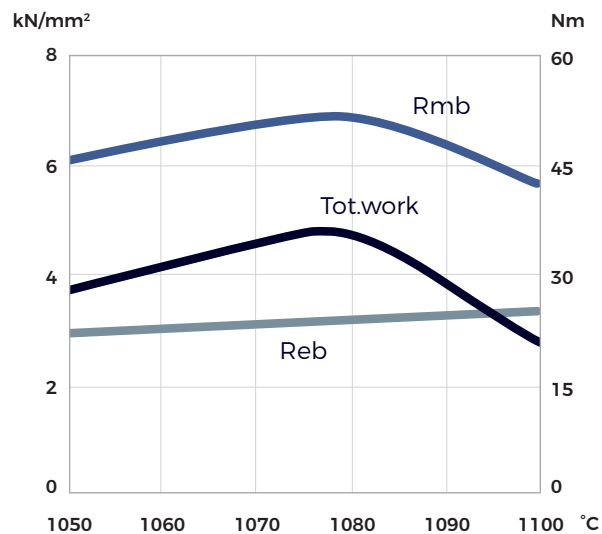

Hardening temperature in °C

Tempering 2 x 1 hour at 560° C  
Dimension of test piece Ø 4.7 mm

Rmb = Ultimate bend strength in kN/mm<sup>2</sup>  
Reb = Bend yield strength in kN/mm<sup>2</sup>  
Tot. work = Total work in Nm

**COMPARATIVE PROPERTIES**

