

# Conventional High-Speed Steel Evoloop® T1

# ERASTEEL

**Evoloop® T1 is a tungsten alloyed high speed steel for abrasive wear applications.**

## STANDARDS

- > EN 10027-1: HS 18-0-1
- > EN 10027-2: 1.3355
- > FRANCE: AFNOR Z80WCV.18.4.1
- > ASTM: AISI T1
- > SWEDEN: SS 2750
- > JIS: SKH2

## DELIVERY HARDNESS

- > Typical soft annealed hardness is 260 HB
- > Cold-drawn and cold-rolled material is typically 10-40 HB harder

## CHEMICAL COMPOSITION

Safety datasheet available

| C    | Cr  | Mo | W    | Co | V   |
|------|-----|----|------|----|-----|
| 0.75 | 4.1 | -  | 18.0 | -  | 1.1 |

## APPLICATIONS

- > Twist drills
- > Taps
- > Milling cutters
- > Wood knives
- > Textile knives
- > Paper knives

## FORM SUPPLIED

- > Flat bars
- > Strips

- > Square bars

Available surface conditions: drawn, ground, hot-rolled, cold-rolled.

## HEAT TREATMENT


- > Soft annealing in a protective atmosphere at 850-900°C for 3 hours, followed by slow cooling 10°C per hour down to 700°C, then air cooling.
- > Stress-relieving at 600°C to 700°C for approximately 2 hours, slow cooling down to 500°C.
- > Hardening in a protective atmosphere with pre-heating in 2 steps at 450-500°C and 850-900°C and austenitising at a temperature suitable for chosen working hardness.
- > Tempering at 560°C twice for at least 1 hour each time.

## PROCESSING

Evoloop® T1 can be worked as follows:

- > machining (grinding, turning, milling)
- > polishing
- > hot forming
- > electrical discharge machining
- > welding (special procedure including preheating and filler materials of base material composition)

## GUIDELINES FOR HARDENING

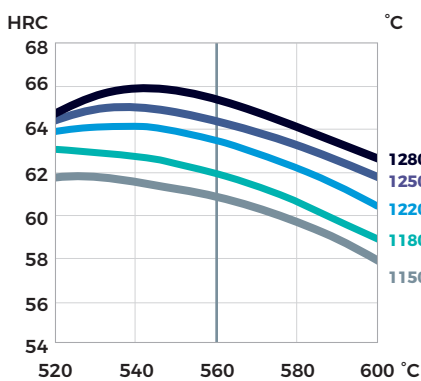

Tempering temperature in °C

Hardness after hardening, quenching and tempering 2 x 1 hour

## GRINDING

During grinding, local heating of the surface, which may alter the temper, must be avoided. Grinding wheel manufacturers can provide advice on the choice of grinding wheels.

## SURFACE TREATMENT

The steel grade is a perfect substrate material for PVD coating. If nitriding is requested, a small diffusion zone is recommended but avoid compound and oxidized layers.


| Tool                      | Hardening   | Tempering |
|---------------------------|-------------|-----------|
| Single-edge cutting tools | 1280°C      | 550-570°C |
| Multi-edge cutting tools  | 1180-1280°C | 550-570°C |
| Cold work tools           | 1150-1200°C | 550-570°C |

**PROPERTIES**

**PHYSICAL PROPERTIES**

|                           |      |
|---------------------------|------|
| Temperature               | 20°C |
| Density g/cm <sup>3</sup> | 8.7  |


**IMPACT TOUGHNESS**

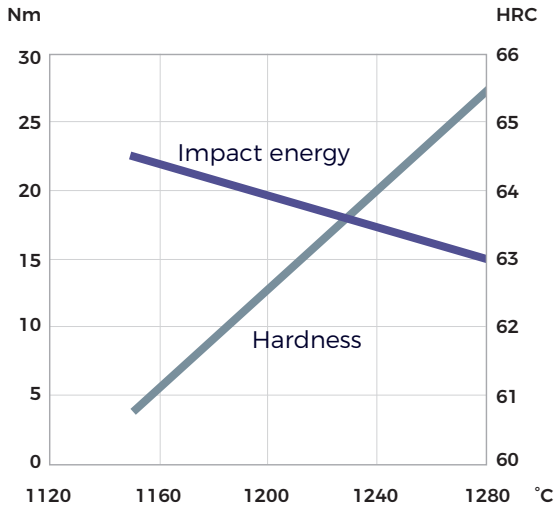

Hardening temperature in °C

Tempering 2 x 1 hour at 560° C  
Unnotched test piece 7 x 10 x 55 mm

**4-POINT BEND STRENGTH**

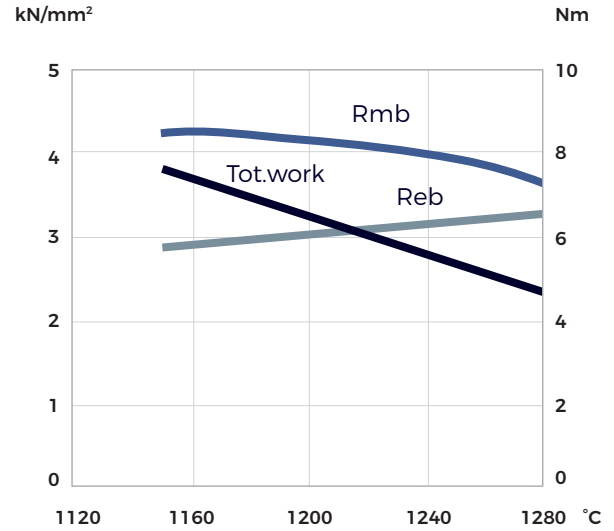

Hardening temperature in °C

Tempering 2 x 1 hour at 560° C  
Dimension of test piece Ø 4.7 mm

Rmb = Ultimate bend strength in kN/mm<sup>2</sup>  
Reb = Bend yield strength in kN/mm<sup>2</sup>  
Tot. work = Total work in Nm

**COMPARATIVE PROPERTIES**

